

UNCLASSIFIED

AD NUMBER
AD432439
NEW LIMITATION CHANGE
TO Approved for public release, distribution unlimited
FROM Distribution authorized to U.S. Gov't. agencies and their contractors; Administrative and Operational Use; Aug 1963. Other requests shall be referred to the Office of Naval Research, 800 North Quincy Street, Arlington, VA 22217.
AUTHORITY
ONR ltr 4 May 1977

THIS PAGE IS UNCLASSIFIED

UNCLASSIFIED

AD 432439

DEFENSE DOCUMENTATION CENTER

FOR

SCIENTIFIC AND TECHNICAL INFORMATION

CAMERON STATION, ALEXANDRIA, VIRGINIA



UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

432439


AD No.

432439

DDC FILE COPY

To be submitted to Physical Review Letters

⑤ 160 800 ⑦

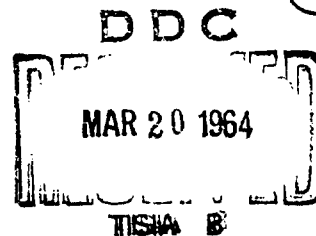

⑩ UPPER CBT
 Superconducting Behavior of Superimposed Thin Films of Al and Sn

⑮ Contract Nonr-23256-105X
 ⑩ P. NR 0183402
 by D. S. Schreiber and W. D. Knight, per Telecom
 IRA Cohen

Department of Physics, University of California, Berkeley

~~It is of interest to study the behavior of superimposed layers of superconducting and non-superconducting metals. We report ~~on~~ nuclear magnetic resonance (NMR) and resistivity measurements ^{are made} on multiple alternating layers of Sn and Al in the temperature range between 1.5^o K and 4.2^o K. The accepted transition temperatures of Al and Sn are 1.2^o K and 3.75^o K, respectively.~~

* Supported in part by the U. S. Office of Naval Research.

† National Science Foundation Fellow (1962-63). Permanent address:
 Department of Physics, Northwestern University, Evanston, Illinois.

8/63

NO.OTS

-1-

WTR

Others¹ have observed a depression of T_c in thin films of Sn or Pb when either is overlaid with Ag or Cu. A theoretical prediction^{2,3} for film thickness less than the coherence length suggests that the specimen should exhibit a single depressed transition temperature characteristic of a diluted superconductor. It is tempting to regard Al above its transition temperature as the counterpart of the normal metal Ag, on which model one might expect a corresponding depression of the T_c of Sn in the Sn-Al combination. Our experimental results on Sn-Al sandwiches are that: $T_c(\text{Sn}) = 3.78^\circ\text{K}$ with a mean deviation among 101 specimens of $\pm 0.03^\circ\text{K}$; the extremal values were 3.68°K and 3.82°K and the width of any one transition was 0.05°K or less; and there is no evidence for a superconducting state in Al above $1.76^\circ \pm 0.20^\circ\text{K}$. These data are consistent with the tunneling experiments of Van Gorp⁴ on similar samples.

Our films were prepared⁵ by alternate evaporation of the separate metals in a vacuum of approximately 10^{-6} mm Hg pressure onto a 0.25×10^{-3} inch mylar sheet, which was cooled to a temperature below 0°C . The thickness of the individual layers varied between 70 and 320 \AA for each metal; the total number of pairs varied from one to forty on each mylar sheet. For the measurement of resistivity a 1×3 cm strip was cut from a mylar sheet, the usual four contacts being made to the metallic samples with silver paint. Approximately one thousand such strips were assembled to form a sample for NMR measurements.

TABLE I. NMR Samples

Sample	Number of pairs on mylar	Upper T_c ($^{\circ}\text{K}$)	Lower T_c ($^{\circ}\text{K}$)	$H_c(0)$ (kilogauss)	Sn film thickness	Al film thickness
1	40	3.78	(*)	4.0	160 \AA	70 \AA
2	1	3.73	1.68	8.5	160 \AA	120 \AA
3	5	3.76	(*)	7.5	160 \AA	240 \AA

(*) Superconducting transitions at the lower temperature, identified as the Al transition, were obscured by a complete transition to zero resistivity at the upper T_c brought about by the high probability of having a conducting path of tin alone in these thicker multiple-layered samples.

NMR signals for Al^{27} , Sn^{117} , and Sn^{119} in sample (1) identified resonances from the respective normal pure metals, resonance shifts, line widths and intensities suggesting no evidence for the formation of solid solutions or compounds of any kind.⁶ Partial flux exclusion and the resulting internal magnetic field inhomogeneity prevented observation of the NMR in the superconducting state for this sample. In samples (2) and (3), however, the Al NMR was observed to have a width and resonance shift characteristic of normal Al down to 1.6 $^{\circ}\text{K}$ in a magnetic field of 4500 gauss (the amount of Sn in these samples was insufficient to provide observable signals at any temperature). Resistivity measurements of these samples

suggest that at least the Sn was superconducting below 3.7°K , and since neither the width nor resonance shift of Al changed, we interpret the measurements to mean that the Al was not superconducting. (Both aluminum⁶ and tin⁷ resonance frequencies are known to decrease slightly in the superconducting states in the pure materials.)

In order to interpret the resistivity measurements satisfactorily we must comment on the structure of the films. It is known⁷ that Sn layers evaporated on mylar consist of platelets approximately 100 \AA in diameter, so that the films are not continuous. We find that a superimposed layer of Al restores the continuity. Furthermore, although an initial layer of Al is continuous, an overlayer of Sn reduces the conductivity. If the initial Al layer is thin, the overlayer of Sn results in a discontinuous film. Apparently local melting of the initial layer of Sn is produced by deposition of the second, and, since neither solid solutions nor inter-metallic compounds exist, we visualize the sample as a conglomeration of small platelets of the separate metals in intimate physical contact. This interpretation is consistent with the measurements of resistivity. Of the 101 samples investigated some 13, primarily those containing the thinnest Sn layers, showed a sharp drop in resistivity at the Sn transition temperature to an intermediate value which remained constant down to approximately 1.76°K , below which the resistivity dropped to zero. The lower temperature varied at most by $\pm 0.2^{\circ}\text{K}$ among the samples, but all the transitions were rather sharp having widths of 0.05°K or less. Of the other 85 samples all but five showed zero resistivity just below the upper temperature; in the five, a single transition to zero resistivity occurred at the lower temperature; in one or two cases no transition was observed.

In view of the likely platelet structure, we assume that the conducting path is divided between the two metals, the upper and lower transition temperatures being associated with Sn and Al, respectively. We note that Giaever and Megerle⁸ also found enhanced T_c for Al up to 1.8°K for the thinnest films. It is important to emphasize that no transitions occurred between the two temperatures cited above. Whether or not the enhanced T_c in Al is to be attributed to an action of the Sn on Al or simply to strains in the latter, the fact remains that the NMR of the Al is typical of the normal metal even when it is proximate to Sn in the superconducting state.

We emphasize that our results pertain to a composite specimen the two components of which do not mutually dissolve or interact to form compounds. The same is not true of previously investigated specimens like Sn-Ag.⁴ Our results suggest that the superconducting properties of the Sn component are not affected by intimate contact with a metal in the normal state. It is probably also true that the Al is not affected by the close proximity of superconducting Sn at least above the lower transition temperature.

For the sake of completeness it should be pointed out that all the thin film samples have characteristically high critical fields, $H_c(0)$ ranging from 3000 to 11,000 gauss; this is convenient for the NMR measurements. Their critical fields also displayed either one of two characteristic angular dependences with respect to the magnetic field direction as discussed by Tinkham,⁹ suggesting a first order transition for those with the lower critical fields, and a second order for those with the highest critical fields.

This work is being continued in order to investigate Cooper's suggestion that the NMR shift of both components may be affected when the entire specimen is superconducting.

We are grateful to Dr. R. H. Hammond of General Atomic, San Diego, for permission to quote his unpublished results on pure Al . We acknowledge with thanks the assistance of W. Henry with some of the measurements. One of us (D.S.S.) wishes to express his appreciation to the Department of Physics of the University of California, Berkeley, for its hospitality during the course of this investigation.

REFERENCES

1. W. A. Simmons and D. H. Douglass, Jr., Phys. Rev. Letters 9, 153 (1962);
P. H. Smith, et al., Phys. Rev. Letters 6, 686 (1961); P. Hilsch, et al., 8th International Congress on Low Temperature Physics, London (1962), p. 169.
2. L. N. Cooper, Phys. Rev. Letters 6, 609 (1961).
3. D. H. Douglass, Jr., Phys. Rev. Letters 9, 155 (1962).
4. G. J. Van Gorp, Physics Letters 5, 303 (1963).
5. G. M. Androes, R. H. Hammond and W. D. Knight, Rev.Sci. Instr. 32, 251 (1961).
6. R. H. Hammond, private communication.
7. G. M. Androes and W. D. Knight, Phys. Rev. 121, 779 (1961).
8. I. Giaever and K. Megerle, Phys. Rev. 122, 1101 (1961).
9. M. Tinkham, Phys. Rev. 129, 2413 (1963).